NATIONAL BUREAU OF STANDARDS REPORT

3186

A METHOD FOR DETERMINING

THE

DIFFUSION COEFFICIENT OF A POROUS MATERIAL

by

Samuel M. Genensky

U. S. DEPARTMENT OF COMMERCE
NATIONAL BUREAU OF STANDARDS

U. S. DEPARTMENT OF COMMERCE
Sinclair Weeks, *Secretary*

NATIONAL BUREAU OF STANDARDS
A. V. Astin, *Director*

THE NATIONAL BUREAU OF STANDARDS

The scope of activities of the National Bureau of Standards is suggested in the following listing of the divisions and sections engaged in technical work. In general, each section is engaged in specialized research, development, and engineering in the field indicated by its title. A brief description of the activities, and of the resultant reports and publications, appears on the inside of the back cover of this report.

Electricity. Resistance and Reactance Measurements. Electrical Instruments. Magnetic Measurements. Electrochemistry.

Optics and Metrology. Photometry and Colorimetry. Optical Instruments. Photographic Technology. Length. Engineering Metrology.

Heat and Power. Temperature Measurements. Thermodynamics. Cryogenic Physics. Engines and Lubrication. Engine Fuels. Cryogenic Engineering.

Atomic and Radiation Physics. Spectroscopy. Radiometry. Mass Spectrometry. Solid State Physics. Electron Physics. Atomic Physics. Neutron Measurements. Infrared Spectroscopy. Nuclear Physics. Radioactivity. X-Ray. Betatron. Nucleonic Instrumentation. Radiological Equipment. Atomic Energy Commission Radiation Instruments Branch.

Chemistry. Organic Coatings. Surface Chemistry. Organic Chemistry. Analytical Chemistry. Inorganic Chemistry. Electrodeposition. Gas Chemistry. Physical Chemistry. Thermochemistry. Spectrochemistry. Pure Substances.

Mechanics. Sound. Mechanical Instruments. Fluid Mechanics. Engineering Mechanics. Mass and Scale. Capacity, Density, and Fluid Meters. Combustion Control.

Organic and Fibrous Materials. Rubber. Textiles. Paper. Leather. Testing and Specifications. Polymer Structure. Organic Plastics. Dental Research.

Metallurgy. Thermal Metallurgy. Chemical Metallurgy. Mechanical Metallurgy. Corrosion.

Mineral Products. Porcelain and Pottery. Glass. Refractories. Enameled Metals. Concreting Materials. Constitution and Microstructure.

Building Technology. Structural Engineering. Fire Protection. Heating and Air Conditioning. Floor, Roof, and Wall Coverings. Codes and Specifications.

Applied Mathematics. Numerical Analysis. Computation. Statistical Engineering.

Electronics. Engineering Electronics. Electron Tubes. Electronic Computers. Electronic Instrumentation. Process Technology.

Radio Propagation. Upper Atmosphere Research. Ionospheric Research. Regular Propagation Services. Frequency Utilization Research. Tropospheric Propagation Research. High Frequency Standards. Microwave Standards.

● Office of Basic Instrumentation

● Office of Weights and Measures.

NATIONAL BUREAU OF STANDARDS REPORT

NBS PROJECT		NBS REPORT
1002-10-1029	March 30, 1954	3186

A METHOD FOR DETERMINING THE DIFFUSION COEFFICIENT OF A POROUS MATERIAL

by

Samuel M. Genensky

Fire Protection Section
Building Technology Division

NBS

U. S. DEPARTMENT OF COMMERCE
NATIONAL BUREAU OF STANDARDS

The publication, rep n part, is prohibited unless permission is ndards, Washington 25, D.C. Such per ort has been specifically prepared if th port for its own use.

Approved for public release by the Director of the National Institute of Standards and Technology (NIST) on October 9, 2015.

A METHOD FOR DETERMINING THE DIFFUSION COEFFICIENT OF A POROUS MATERIAL

Abstract

A mathematical analysis based upon Fick's law is developed for a spherical body exposed to an atmosphere with a time invariant moisture concentration. An analytic solution is obtained from which diffusion coefficients may be computed.

1. INTRODUCTION

The fire endurance of many structures is greatly dependent on the amount of water adsorbed on the surface and within the capillary pores of the material of which the structure is formed. This moisture content is a function of both the pore structure of the material, its afinity for water and the moisture vapor pressure present in the ambient atmosphere within which the specimen is conditioned. Many studies have been made of the equilibrium moisture content of woods and textile fibers, as well as portland cement pastes. However, little work appears to have been done on concrete and as a result it seems worth while to perform a few exploratory tests on representative concrete specimens for the purpose of obtaining some indication of the moisture content of concretes prepared in the same fashion and dried to equilibrium under controlled ambient conditions. In planning these experiments it appeared that by proper selection of specimen shape and method of test, it would be possible to obtain moisture diffusion coefficients with very little additional effort. The present report outlines the mathematical reasoning which appears to justify this phase of the proposed work.

2. ASSUMPTIONS

It was proposed that the experiments would permit the measurement or calculation of the following for the specimen under examination:

W_o the weight of the specimen when completely dry

W_1 the equilibrium weight of the specimen exposed to an atmosphere containing moisture at a constant concentration C_o.

$W_2(t)$ the weight of the specimen, a function of time t, exposed to an atmosphere containing moisture at a constant concentration C_1. $W_1 = W_2(t_o)$, t_o being the time the specimen is first exposed to this atmosphere.

$W_2 = W_2(t)$ $t \geq T$ the equilibrium weight of the specimen exposed to the atmosphere containing moisture at a constant concentration C_1. T is the time at which an increase in the specimen's weight can no longer be detected by the experimental apparatus.

A mathematical model based upon Fick's law which utilizes this information to obtain an estimate of the diffusion coefficient is available for a spherical specimen of radius R, throughout which the concentration of the moisture depends upon the radial distance from the center of the specimen and upon the time that the specimen has been exposed to the atmosphere containing moisture at a constant concentration C_1. This same analysis is equally applicable to a hemispherical specimen whose flat surface is completely insulated against moisture flow because here also the concentration of the moisture in the specimen again depends upon the radial distance from the center of the specimen and upon the time. For this model the solution is one-half that for the sphere.

No attempt is made to account for heats of adsorption or desorption in the following analysis.

3. ANALYSIS

Mathematically the problem becomes:

$$\frac{1}{D}\frac{\partial C}{\partial t} = \frac{\partial^2 C}{\partial r^2} + \frac{2}{r}\frac{\partial C}{\partial r} \qquad (0 < r < R,\ t > t_o) \qquad (1)$$

$$C = C_2 \qquad (0 \leq r \leq R,\ t = t_o) \qquad (2)$$

$$C = C_3 \qquad (r = R,\ t > t_o) \qquad (3)$$

$$C \neq \infty \qquad (r = 0,\ t \geq t_o) \qquad (4)$$

where r is the radial distance measured from the center of the sphere. cm.

t is the time measured from the instant the specimen is exposed to the atmosphere containing moisture at a constant concentration C_1. sec.

$C=C(r,t)$ is the concentration of the moisture in the specimen and is a function of both radial distant r and time t. gm/cm^3

D is the diffusion constant for the specimen. $cm^2/sec.$

$C_2 = \frac{W_1 - W_o}{\frac{4}{3}\pi R^3}$ C_2 is the concentration in gm/cm^3 of the moisture in the specimen when it is introduced into the atmosphere containing moisture at a constant concentration C_1.

$C_3 = \frac{W_2 - W_o}{\frac{4}{3}\pi R^3}$ C_3 is the concentration in gm/cm^3 of the moisture in the specimen when it reaches equilibrium in the atmosphere containing moisture at a constant concentration C_1.

No generality will be lost if t_o is taken equal to zero. Condition (4) guarantees that the concentration remains finite at the center of the sphere in compliance with physical requirements.

Let $V = V(r,t) = C(r,t) - C_3$ (5)

Using (5) and recalling that t_o has been set equal to zero, (1) - (4) become

$$\frac{1}{D}\frac{\partial V}{\partial t} = \frac{\partial^2 V}{\partial r^2} + \frac{2}{r}\frac{\partial V}{\partial r} \qquad (0<r<R,\ t>0) \qquad (6)$$

$$V = C_2 - C_3 \qquad (0 \leq r \leq R,\ t = 0) \qquad (7)$$

$$V = 0 \qquad (r = R,\ t>0) \qquad (8)$$

$$V \neq \infty \qquad (r = 0,\ t \geq 0) \qquad (9)$$

let $V = V(r,t) = \rho(r)\,\tau(t) = \rho\tau$ (10)

then $\frac{\partial V}{\partial t} = \rho\tau'$, $\frac{\partial V}{\partial r} = \rho'\tau$ and $\frac{\partial^2 V}{\partial r^2} = \rho''\tau$ (11)

Substituting these expressions into (6) and multiplying the resulting expression by $1/\rho\tau$ yields:

$$\frac{1}{D}\frac{\tau'}{\tau} = \frac{\rho''}{\rho} + \frac{2}{r}\frac{\rho'}{\rho} \qquad (0<r<R,\ t>0) \qquad (12)$$

Let $\frac{1}{D}\frac{\tau'}{\tau}$ equal $-\lambda^2$ where λ is real (13)

Therefore $\tau' + \lambda^2 D\tau = 0$ (14)

and thus $\tau = ae^{-\lambda^2 Dt}$ where a is an arbitrary constant (15)

Now by (13) $\frac{\rho''}{\rho} + \frac{2}{r}\frac{\rho'}{\rho} = -\lambda^2$ (16)

and thus $\rho'' + \frac{2}{r}\rho' + \lambda^2\rho = 0$ (17)

Let $S = r\rho$ (18)

Using (18), (17) becomes

$$S'' + \lambda^2 S = 0 \quad (19)$$

and thus $\rho = A\frac{\cos\lambda r}{r} + B\frac{\sin\lambda r}{r}$ where A and B are arbitrary constants (20)

Now since $\lim_{r\to 0}\frac{\cos\lambda r}{r} \longrightarrow \infty$, A = 0 for otherwise (9) would be contradicted.

Thus $$V(r,t) = Pe^{-\lambda^2 Dt}\frac{\sin\lambda r}{r} \quad \text{where } P = aB \quad (21)$$

Now in view of (8) $\sin\lambda R = 0$ (22)

and thus $\lambda = \frac{n\pi}{R}$ $n = 0, \pm 1, \pm 2, \ldots$ (23)

Therefore (21) may be written

$$V(r,t) = \sum_{n=-\infty}^{\infty} P_n e^{-\frac{\pi^2 Dt}{R^2}n^2}\frac{\sin\frac{n\pi}{R}r}{r} \quad (24)$$

$$= \sum_{n=1}^{\infty} Q_n e^{-\frac{\pi^2 Dt}{R^2}n^2}\sin\frac{n\pi r}{r} \quad \text{where } Q_n = P_n - P_{-n} \quad (25)$$

$n = 1, 2, \ldots$

Considering (7) and (25) and recalling Fourier series analysis

$$(C_2 - C_3)r = \sum_{n=1}^{\infty} Q_n \mathrm{Sin}\frac{n\pi r}{R} \tag{26}$$

and thus

$$Q_n = \frac{2}{R}\int_o^R (C_2-C_3)r\ \mathrm{Sin}\frac{n\pi r}{R}\ dr \tag{27}$$

Integrating (27)

$$Q_n = \frac{2(C_2-C_3)R}{\pi}\ \frac{(-1)^{n+1}}{n} \tag{28}$$

Thus

$$V(r,t) = \frac{2(C_2-C_3)R}{\pi}\sum_{n=1}^{\infty}\frac{(-1)^{n+1}}{n} e^{-\frac{\pi^2 Dt}{R^2}n^2}\ \mathrm{Sin}\frac{n\pi r}{R}/r \tag{29}$$

Now the total moisture content of the sphere is found by integrating V(r,t) over the volume of the sphere. Thus

$$4\pi\int_o^R V(r,t)r^2dr = 4\pi\int_o^R \left[\bar{C}(r,t) - C_3\right]r^2dr \tag{30}$$

and

$$4\pi\int_o^R C(r,t)r^2dr = \frac{4}{3}\pi R^3 C_3 + 8(C_2-C_3)R\sum_{n=1}^{\infty}\frac{(-1)^{n+1}}{n} e^{-\frac{\pi^2 Dt}{R^2}n^2}\int_o^R r\mathrm{Sin}\frac{n\pi r}{R}\ dr \tag{31}$$

Integrating (31)

$$4\pi\int_o^R C(r,t)r^2dr = \frac{4}{3}\pi R^3 C_3 + \frac{8(C_2-C_3)R^3}{\pi}\sum_{n=1}^{\infty}\frac{1}{n^2} e^{-\frac{\pi^2 Dt}{R^2}n^2} \tag{32}$$

and for a hemispherical specimen

$$2\pi\int_o^R C(r,t)r^2dr = \frac{2}{3}\pi R^3C_3 + \frac{4(C_2-C_3)R^3}{\pi}\sum_{n=1}^{\infty}\frac{1}{n^2}e^{-\frac{\pi^2Dtn^2}{R^2}} \qquad (33)$$

Now

$4\pi\int_o^R C(r,t)r^2dr$ is the weight of the moisture in the specimen

at time t (where t = 0 denotes the moment the specimen is placed into the atmosphere containing moisture at a constant concentration C_1). Therefore

$$4\pi\int_o^R C(r,t)r^2dr = W_2(t) - W_o \qquad 0 \leqslant t < \infty \qquad (34)$$

Recalling the definitions of C_2 and C_3

$$\frac{4}{3}\pi R^3C_3 = W_2 - W_o \qquad t \geqslant T \qquad (35)$$

and $$\frac{4}{3}\pi R^3C_2 = W_1 - W_o \qquad (36)$$

Recalling that $\sum_{n=1}^{\infty}\frac{1}{n^2} = \frac{\pi^2}{6}$ and (34)-(36), (33) becomes

$$W_2(t) - W_o = W_2 - W_o + \left[(W_1-W_o)-(W_2-W_o)\right]\frac{6}{\pi^2}\sum_{n=1}^{\infty}\frac{1}{n^2}e^{-\frac{\pi^2Dtn^2}{R^2}} \qquad (37)$$

and thus

$$\frac{W_2(t) - W_2}{W_1 - W_2} = \frac{6}{\pi^2}\sum_{n=1}^{\infty}\frac{1}{n^2}e^{-\frac{\pi^2Dt}{R^2}n^2} \qquad (38)$$

Let $$f\left(\frac{\pi^2 Dt}{R^2}\right) = \frac{6}{\pi^2} \sum_{n=1}^{\infty} \frac{1}{n^2} e^{-\frac{\pi^2 Dt}{R^2} n^2} \tag{39}$$

and (38) becomes

$$\frac{W_2(t) - W_2}{W_2(0) - W_2} = f\left(\frac{\pi^2 Dt}{R^2}\right) \text{ recalling that } W_1 = W_2(0). \tag{40}$$

Since $W_2(t)$, $W_2(0)$, W_2, t and R are known, (40) can thus be solved for the diffusion coefficient D. Figure 1 which is a plot of $f\left(\frac{\pi^2 Dt}{R^2}\right)$ against $\frac{\pi^2 Dt}{R^2}$ has been included to ease the labor in the evaluation of D.

For $\frac{\pi^2 Dt}{R^2} \geq 2$

$$\frac{f\left(\frac{\pi^2 Dt}{R^2}\right) - \frac{6}{\pi^2} e^{-\frac{\pi^2 Dt}{R^2}}}{f\left(\frac{\pi^2 Dt}{R^2}\right)} < 0.001$$

and thus the simpler expression $\frac{6}{\pi^2} e^{-\frac{\pi^2 Dt}{R^2}}$ becomes a very good approximation to $f\left(\frac{\pi^2 Dt}{R^2}\right)$ over that range.

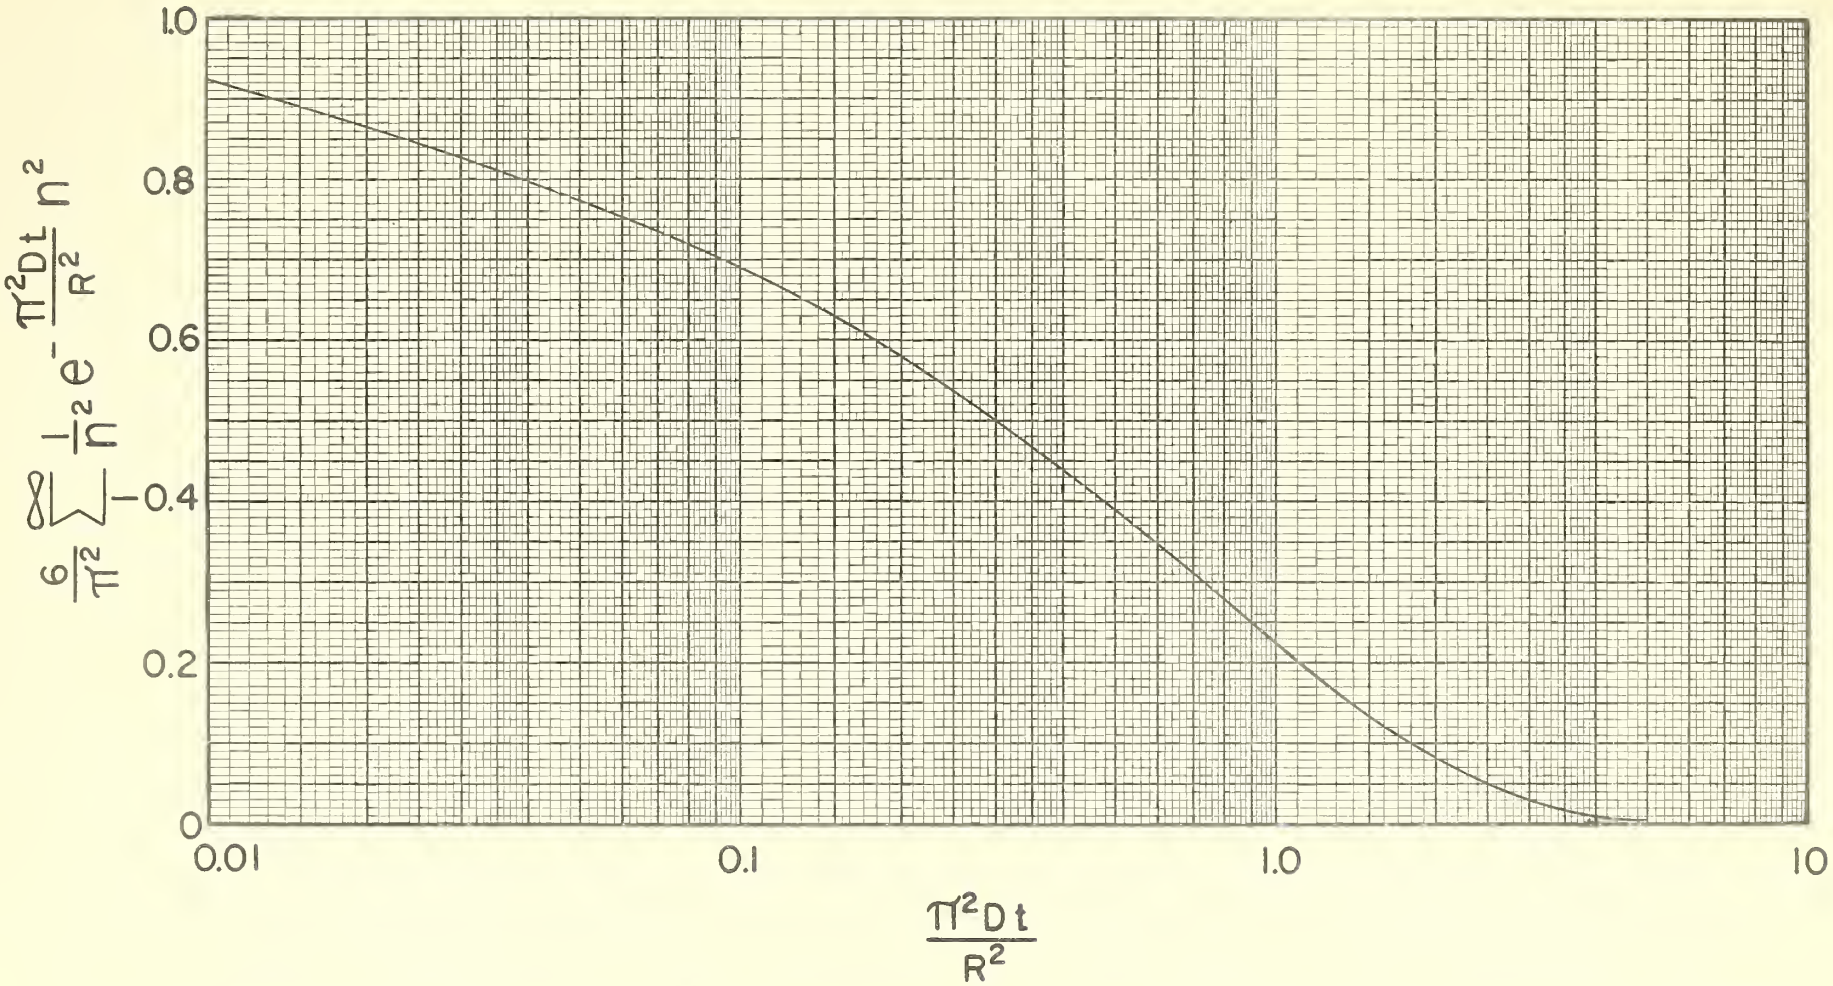

FIG. 1 RATIO OF UNACCOMPLISHED ABSORPTION TO TOTAL POSSIBLE ABSORPTION VS $\frac{\pi^2 D t}{R^2}$

THE NATIONAL BUREAU OF STANDARDS

Functions and Activities

The functions of the National Bureau of Standards are set forth in the Act of Congress, March 3, 1901, as amended by Congress in Public Law 619, 1950. These include the development and maintenance of the national standards of measurement and the provision of means and methods for making measurements consistent with these standards; the determination of physical constants and properties of materials; the development of methods and instruments for testing materials, devices, and structures; advisory services to Government Agencies on scientific and technical problems; invention and development of devices to serve special needs of the Government; and the development of standard practices, codes, and specifications. The work includes basic and applied research, development, engineering, instrumentation, testing, evaluation, calibration services, and various consultation and information services. A major portion of the Bureau's work is performed for other Government Agencies, particularly the Department of Defense and the Atomic Energy Commission. The scope of activities is suggested by the listing of divisions and sections on the inside of the front cover.

Reports and Publications

The results of the Bureau's work take the form of either actual equipment and devices or published papers and reports. Reports are issued to the sponsoring agency of a particular project or program. Published papers appear either in the Bureau's own series of publications or in the journals of professional and scientific societies. The Bureau itself publishes three monthly periodicals, available from the Government Printing Office: The Journal of Research, which presents complete papers reporting technical investigations; the Technical News Bulletin, which presents summary and preliminary reports on work in progress; and Basic Radio Propagation Predictions, which provides data for determining the best frequencies to use for radio communications throughout the world. There are also five series of nonperiodical publications: The Applied Mathematics Series, Circulars, Handbooks, Building Materials and Structures Reports, and Miscellaneous Publications.

Information on the Bureau's publications can be found in NBS Circular 460, Publications of the National Bureau of Standards ($1.25) and its Supplement ($0.75), available from the Superintendent of Documents, Government Printing Office. Inquiries regarding the Bureau's reports and publications should be addressed to the Office of Scientific Publications, National Bureau of Standards, Washington 25, D. C.

NBS